

Polyaniline and its composites with carbon nanomaterials: preparation, properties, application

© Irina V. Gutnik^a✉, Tatyana P. Dyachkova^a, Elena A. Burakova^a,
Evgeniy N. Tugolukov^a, Artem V. Rukhov^a, Georgiy A. Titov^a

^a Tambov State Technical University, Bld. 2, 106/5, Sovetskaya St., Tambov, 392000, Russian Federation

✉ i.v.gutnik@yandex.ru

Abstract: The increased attention of researchers to electrically conductive polymers, including polyaniline (PANI), is due to the wide possibilities of its use in the production of supercapacitors, energy storage devices, anticorrosive coatings, detectors, sensors, solar cells, antimicrobial materials, sorbents, and coatings that absorb electromagnetic radiation. However, the instability of the PANI properties during operation limits the practical use of the polymer. In this regard, to date, many attempts have been made to stabilize the characteristics and increase the service life of polyaniline. Thus, new composite materials, which combine PANI and one or more other components, including carbon nanomaterials (carbon nanotubes, graphene, graphene oxide, reduced graphene oxide, mesoporous carbon), montmorillonite, metals, chalcogenides, conductive polymers, were developed. The purpose of this study is to summarize the information accumulated to date on electrically conductive polyaniline and its composites with carbon nanomaterials (CNM), as well as to demonstrate their potential and future prospects. The paper describes the structure and properties of the polymer. Chemical and electrochemical approaches to the synthesis of PANI and composites based on it are considered, attention is paid to the influence of synthesis conditions on the structure and properties of the final reaction products. A brief description of the application of polyaniline and its composites with CNM is given.

Keywords: polyaniline; carbon nanotubes; functionalized carbon nanotubes; graphene; composite.

For citation: Gutnik IV, Dyachkova TP, Burakova EA, Tugolukov EN, Rukhov AV, Titov GA. Polyaniline and its composites with carbon nanomaterials: preparation, properties, application. *Journal of Advanced Materials and Technologies*. 2024;9(2):132-151. DOI: 10.17277/jamt.2024.02.pp.132-151

Полианилин и его композиты с углеродными наноматериалами: получение, свойства, применение

© И. В. Гутник^a✉, Т. П. Дьячкова^a, Е. А. Буракова^a,
Е. Н. Туголуков^a, А. В. Рухов^a, Г. А. Титов^a

^a Тамбовский государственный технический университет,
ул. Советская, 106/5, пом. 2, Тамбов, 392000, Российская Федерация

✉ i.v.gutnik@yandex.ru

Аннотация: Повышенное внимание исследователей к электропроводящим полимерам, в том числе к полианилину (ПАНИ), обусловлено широкими возможностями его применения при производстве суперконденсаторов, накопителей энергии, антикоррозионных покрытий, датчиков, сенсоров, элементов солнечных батарей, антимикробных материалов, сорбентов, покрытий, поглощающих электромагнитное излучение. Однако нестабильность свойств ПАНИ в ходе эксплуатации ограничивает практическое применение полимера. В связи с этим к настоящему времени предпринято множество попыток, позволяющих стабилизировать характеристики и увеличить срок службы полианилина. Например, разработаны новые композиционные материалы, сочетающие в себе ПАНИ и один или несколько других компонентов, среди которых углеродные наноматериалы (углеродные нанотрубки, графен, оксид графена, восстановленный оксид графена, мезопористый углерод), монтмориллонит, металлы, халькогениды, проводящие полимеры. Цель исследования – обобщить сведения, накопленные к настоящему времени об электропроводящем полианилине и его композитах с углеродными наноматериалами (УНМ), продемонстрировать их потенциал и будущие перспективы. Даны описания строения и свойств полимера.

Рассмотрены химические и электрохимические подходы к синтезу ПАНИ и композитов на его основе, уделено внимание влиянию условий синтеза на структуру и свойства конечных продуктов реакции. Дана краткая характеристика областей применения полианилина и его композитов с УНМ.

Ключевые слова: полианилин; углеродные нанотрубки; функционализированные углеродные нанотрубки; графен; композит.

Для цитирования: Gutnik IV, Dyachkova TP, Burakova EA, Tugolukov EN, Rukhov AV, Titov GA. Polyaniline and its composites with carbon nanomaterials: preparation, properties, application. *Journal of Advanced Materials and Technologies*. 2024;9(2):132-151. DOI: 10.17277/jamt.2024.02.pp.132-151

1. Introduction

Since the discovery of polyaniline (PANI), which belongs to the class of electrically conductive polymers, to the present time there has been an increase in the number of studies related to this material. This is primarily due to the unique properties of PANI [1]. PANI belongs to the class of conjugated polymers, so it can have conductivity close to metallic. PANI is also distinguished by ease of synthesis and doping with protic acids, environmental stability and low cost [2–4]. However, changes in electrical conductivity during operation, low cyclic stability, mechanical degradation, and processing complexity significantly limit the practical use of the polymer [5, 6]. It is known that charge/discharge processes are accompanied by swelling, shrinkage and destruction of the polymer during doping/dedoping processes, which leads to a decrease in cycle stability. In addition, PANI degradation can occur at relatively high potentials. The consequence of this is the low operating potential of PANI electrodes.

To eliminate the above defects, researchers usually combine polyaniline with other materials (carbon nanotubes (CNTs), graphene (G), graphene oxide (GO), cellulose, montmorillonite, metal oxides). As a result, new materials are obtained, which are characterized by increased capacitive characteristics and high chemical stability [7]. For example, a PANI composite with carbon nanotubes, synthesized for use as an electrode material for a supercapacitor, demonstrates a fairly high specific capacitance of $1266 \text{ F} \cdot \text{g}^{-1}$, exceeding the capacitance of the original components [8]. It has also been shown that PANI/CNT hybrids exhibit a synergistic effect [9].

On the one hand, the carbon dispersed carrier increases the accessible surface of PANI, on the other hand, it creates an electrically conductive frame, which makes it possible, by increasing electronic and ionic conductivity, to increase the electrical power removed from the electrode. Also, this framework is more rigid than PANI itself, which makes it possible to stabilize the porous structure of the polymer with multiple repetition of charge/discharge.

The possibility of stabilizing the PANI properties by synthesizing composites based on it gives rise to a large number of studies on this topic, the results of which are reflected in both scientific and review articles. However, in the latter, there is mainly a generalization of the results obtained within specific areas of practical application of composites (for example, in supercapacitors, sorbents). With this approach, the effectiveness of the synthesized composites is demonstrated in only one area of application. There is also no systematic information on the dependence of the characteristics of composites on their composition. In this regard, this review summarizes the results accumulated to date in the field of preparation and characterization of PANI composites with carbon nanomaterials. Attention is paid to the influence of the mass composition of composites on their morphological and operational characteristics. A brief description of promising areas of application of these composites is presented. The review also provides information on the structure, properties and methods of producing PANI, which can be used by researchers to select optimal conditions for the synthesis of composites with given parameters.

2. Chemical structure and properties of PANI

PANI has the longest history of research among electrically conductive polymers. This polymer was discovered in the middle of the 19th century [10]. It was then known as “aniline black” (a term in those days used for any product obtained by the oxidation of aniline). The discovery of PANI can probably be considered the experiments of Runge [11]. Later, Fritsche and Leteby continued to study the oxidation process of aniline and discovered a change in the color of the resulting precipitate [12–14]. The results obtained by scientists in the century before last served as a prerequisite for studying the process of obtaining “black aniline”, as well as for studying its redox and acid-base transformations.

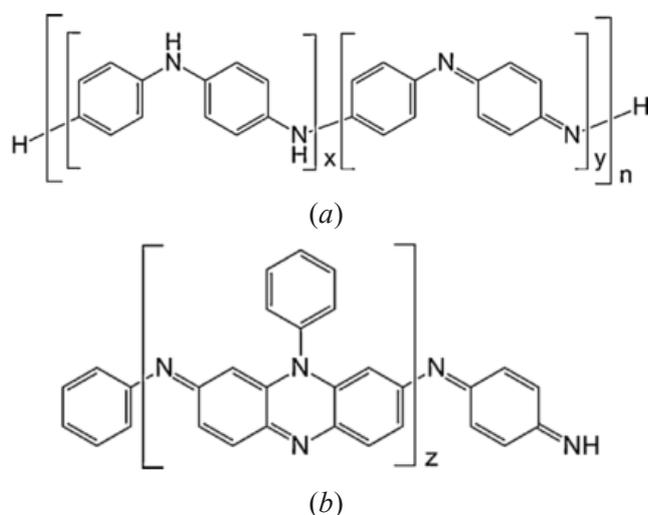


Fig. 1. Molecular structure of various redox forms of linear aniline octamers, proposed at the beginning of the 20th century
 (a: $x + y = 4$, $n = 1$; leucoemeraldine: $x = 4$, $y = 0$;
 protoemeraldine: $x = 3$, $y = 1$; emeraldine: $x = 2$, $y = 2$;
 nigraniline: $x = 1$, $y = 3$; pernigraniline: $x = 0$, $y = 4$)
 and black aniline (b: $z = 3$) [15]

The terms emeraldine and nigraniline were coined for the various oxidized/reduced forms of aniline black. At the beginning of the 20th century, the concepts “leucoemeraldine”, “protoemeraldine” and “pernigraniline” were introduced to designate linear combinations of aniline octamers with varying degrees of oxidation, i.e. with different numbers of N-phenylbenzoquinonediimine and 4-aminodiphenylamine fragments in the main chain (Fig. 1a) [15].

The molecular weight of PANI in the form of emeraldine is significantly higher than that of octamers, indicating the existence of intermediate oxidation states between leucoemeraldine and emeraldine ($x > y$, $y \geq 1$, Fig. 1a), which could be designated as protoemeraldine, corresponding to $x/y \sim 3$, as well as between emeraldine and pernigraniline ($x < y$, $x \geq 1$, Fig. 1a), which can be designated as nigraniline, as in the case of $x/y \sim 1/3$ [16].

In 1965, information that emeraldine has high conductivity appeared [17]. At the end of the last century, scientists discovered the possibility of transitioning from one form of PANI to another. For example, emeraldine can be converted from a base to a salt. This process is accompanied by a color change from blue to green (Fig. 2). Based on the results of these studies, a paper was published where it was reported that the transition of emeraldine to this state is accompanied by a sharp increase in conductivity by more than 10 orders of magnitude – up to $1\text{--}5 \text{ S}\cdot\text{cm}^{-1}$ [18].

Multiple studies conducted over the past decades allow us to conclude that the emeraldine salt of PANI (PANI-ES) contains localized/delocalized radical cations (polarons) and dication (bipolarons) in different proportions. Their content depends on the synthesis conditions and isolation procedures [19] (Fig. 2).

The transition of PANI in the form of emeraldine base (PANI-EB) to PANI-ES is carried out using doping, which can be done in two ways: oxidation (p-doping, when the doping component accepts electrons) or reduction (n-doping - the doping component gives up electrons) neutral polymer with a modifying additive [4].

Proton donors, usually acids (hydrochloric, sulfuric, sulfonic acids, etc.) are used to dope PANI. The electrical conductivity of doped PANI can be influenced by a number of factors, including the oxidation state of the polymer, the type of protic acid, the degree of protonation, the moisture content of the polymer, and the morphology of the polymer chain [20].

3. Methods for obtaining PANI

Currently, there are several methods for obtaining PANI. The most common one is the oxidative polymerization of aniline. There are chemical [21–24], electrochemical [25], and enzymatic [26] polymerization.

During chemical synthesis in an acidic environment, the aniline monomer or salt (aniline hydrochloride or sulfate) is converted into a conjugated polymer. Distinctive features of this method are the high yield of the target reaction product (about 90–95 % of the theoretically calculated one), as well as the relatively high electrical conductivity ($1\text{--}5 \text{ S}\cdot\text{cm}^{-1}$) of the synthesized material [4].

To date, significant experimental material has been accumulated on the relationship between the properties of PANI obtained by chemical polymerization and synthesis conditions. Among the synthesis parameters that most significantly influence the properties of the final product are the nature of the oxidizing agent, pH, concentration of reagents, and polymerization temperature [27, 28].

It is known that PANI can have different morphologies (nanofibers, nanorods, nanotubes, nanospheres, granules). It has been proven that it depends on the nature of the oxidizing agent or the presence of additives in the reaction mixture [29]. For example, by varying the synthesis conditions, it is possible to obtain PANI with a granular structure [30], and in a weakly acidic environment, PANI is obtained in the form of nanotubular particles [31].

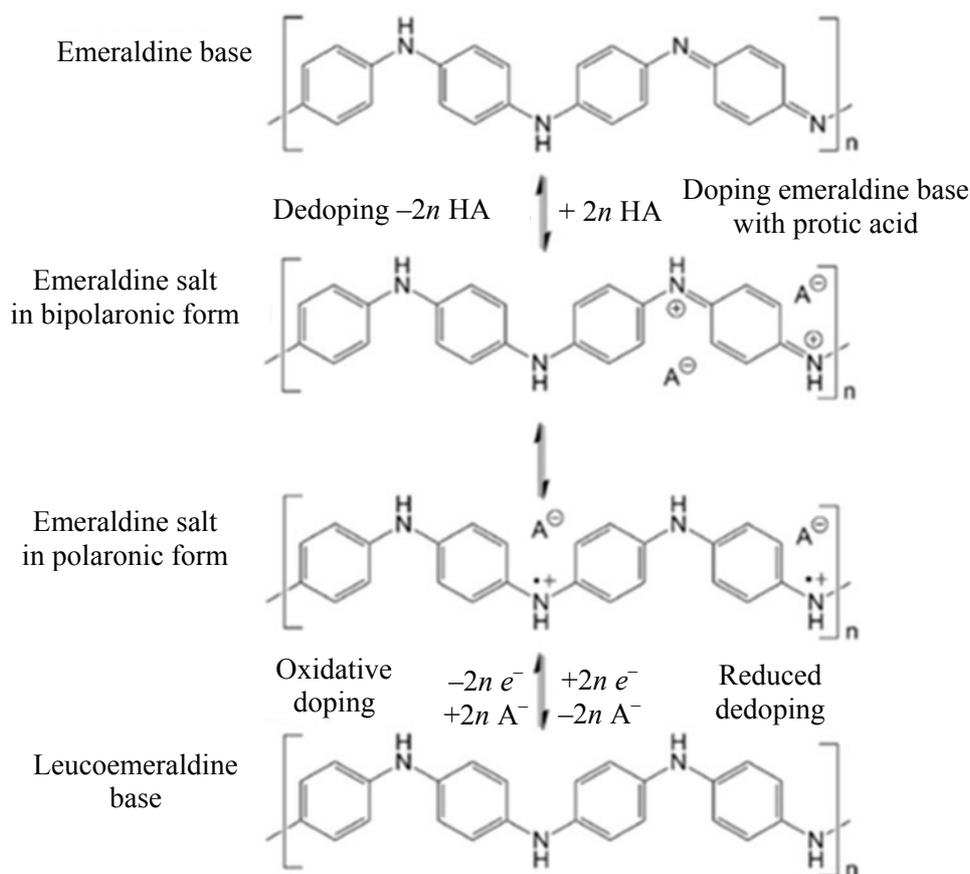


Fig. 2. Oxidative doping of leucoemeraldine base and doping emeraldine base with protic acid; A is anion

Various PANI structures are characterized by a set of morphological features (shape of structural units, specific surface area, pore size), which determine the accessibility of PANI macromolecules to electrolyte ions, and the electronic and redox properties determine the maximum possible power and energy intensity of devices based on it [32–34].

The main methods for carrying out electrochemical synthesis are galvanostatic (at a constant current) [35–37], potentiostatic (at a constant electrochemical potential) [38] and potential cycling modes [39]. The yield, morphology, electrochemical behavior, adhesion to the electrode, optical properties and other characteristics of the PANI film obtained by electrosynthesis are determined by polymerization conditions, such as the type and concentration of the electrolyte, the nature of the electrode, and synthesis modes [35].

Most often, the electrochemical synthesis of PANI is based on the anodic oxidation of aniline at various electrodes. This is due to the possibility of obtaining a purer polymer without oxidizing agent impurities, as well as the possibility of controlling the thickness of the film and observing the process of its formation using various physical and chemical methods (optical, electrochemical, etc.). Moreover,

the molecular weight of PANI synthesized by electrochemical polymerization methods is usually lower than that of chemical synthesis [40].

Compared to chemical polymerization, electrochemical synthesis is faster and does not require the use of oxidizing agents and additives. The advantages of the method also include the ability to regulate the conditions (potential and current) of PANI deposition and the almost complete absence of by-products. At the same time, the morphological forms of PANI are not so diverse: nanofibers, nanogranules, or thin films on the surface of the substrate [41–43].

However, the electrochemical method is only suitable for producing polymer in small quantities, while the chemical method allows the production of polymer in large volumes [44].

The processes of converting aniline into PANI during chemical and electrochemical polymerization are similar to each other and occur in several stages (Table 1) [30].

As findings show, the duration of the induction period depends on the synthesis conditions and can increase with a decrease in the initial temperature of aniline oxidation or shorten with increasing acid concentrations [45].

Table 1. Characteristics of the stages of aniline oxidative polymerization

Stage	Observed phenomena	Products formed
Rapid exothermic oxidation of neutral aniline molecules	Increase in temperature, decrease in pH	Non-conducting oligomers
Induction period	Temperature remains virtually unchanged, pH decreases moderately	Aniline trimers
Rapid polymerization of anilinium cations	Rapid heat release is accompanied by the formation of protons	Oligomeric and polymeric products

The induction period also becomes shorter when the reacting mixture contains an inert solid material with a high surface area (carbon nanotubes, graphite) [46]. This is explained by the phenomenon of adsorption of oligomers and the formation of nucleates on such substrates.

The decrease in pH during oxidative polymerization is explained as follows: during the formation of bonds between aniline molecules and oligomers or polymers, hydrogen atoms are eliminated in the form of protons and form sulfuric acid with the persulfate reduction product [47–51].

The course of the reaction and the nature of the final product (structure, physicochemical properties, redox form) are influenced by factors such as the acidity of the medium, the nature and concentration of the oxidizing agent.

Aniline oxidation can be started in an acidic or alkaline environment. In this case, some phases may be absent depending on the initial pH of the reacting mixture. If oxidation begins in an alkaline environment, oligomers quickly form and the reaction mass becomes brown.

Conductive forms of PANI are formed in an acidic environment. In this case, practically no exothermic formation of brown oligomers is observed. A low concentration of neutral aniline molecules slows down the formation of short oligomers (mainly semidine dimers). The light blue color visible at this stage is due to the formation of an oxidized dimer. Semidines subsequently participate in the formation of trimers (nucleates), which become initiation centers for the growth of PANI chains. As a result, the polymer is the main product of the reaction; oligomers are present only in minor quantities [52].

The nature of the oxidizing agent, especially its redox potential, has a significant impact on the morphology and properties of PANI [53]. Persulfates (ammonium persulfate and potassium persulfate [54–58] and iron chloride FeCl_3 [59–62] are most often used as oxidizing agents in the synthesis of

PANI. However, when using FeCl_3 , polymerization proceeds at a lower rate, since its redox potential (0.77 V) is lower than that of ammonium persulfate (2.0 V) [63]. However, ammonium persulfate also has disadvantages: it is stoichiometrically consumed in the reaction, which leads to the formation of acidic by-products during the synthesis of the polymer [64]. For environmentally friendly synthesis of PANI, the use of FeCl_3 and ozone as a catalyst and oxidizer, respectively, has been proposed [65]. The only byproduct formed during the reaction under these conditions is water.

When ammonium persulfate is used as an oxidizing agent, the molar ratio “aniline: ammonium persulfate” (r) has a different effect on the yield, elemental composition, electrical conductivity and degree of oxidation of the resulting product. At $r \leq 1.15$, the characteristics of PANI are practically independent of the molar ratio. At $r > 1.15$, overoxidation of PANI accompanied by a decrease in the yield of the polymer, its conductivity, and a noticeable change in its morphology [66] is observed. The optimal molar ratio “aniline: ammonium persulfate” is 1 : 1.25 [4]. An increase in the concentration of ammonium persulfate by two times compared to the concentration of aniline leads to the rupture of polymolecular chains, the formation of quinoid compounds and overoxidized forms of PANI. The use of ammonium persulfate in an amount less than half that of aniline causes a decrease in the yield of PANI to 40–50 %. A number of authors believe [22, 67] that ammonium persulfate is involved in the processes of both initiation and growth of chains.

A number of other compounds are also used as oxidizing agents: manganese oxides [68–70], potassium (VI) dichromate $\text{K}_2\text{Cr}_2\text{O}_7$ [71], cerium (IV) sulfate $\text{Ce}(\text{SO}_4)_2$ [72], copper (II) chloride CuCl_2 [73], copper (II) nitrate $\text{Cu}(\text{NO}_3)_2$ [74], potassium ferricyanide ($\text{K}_3(\text{Fe}(\text{CN})_6)$) [75] and

sodium vanadate (NaVO_3) [76]. Compounds of noble metals (Au (II), Pt (IV), Pd (II), Ag (I)) [77], hydrogen peroxide [78, 79], potassium permanganate [80, 81] are also used as oxidizing agents.

In the case of using oxidizing agents such as cerium (IV) sulfate and potassium dichromate at higher concentrations ($r > 1.15$), a complexation reaction probably occurs, which leads to the production of products containing a large percentage of the metal [66].

There is information about the use of a mixture of oxidizing agents, including $\text{FeCl}_3 / \text{H}_2\text{O}_2$ [82] and $\text{KIO}_3 / \text{NaClO}$ [83]. To accelerate the synthesis of PANI, researchers resorted to the use of catalysts, which are enzymes, for example, horseradish peroxidase [84], enzymes of the oxidoreductase class [85].

A number of researchers propose unconventional methods for the synthesis of PANI: polymerization of aniline under the influence of X-ray irradiation in the presence of nitrate ions [86]; dispersion polymerization in a weak magnetic field [87]; matrix synthesis of PANI on a solid support [88]; oxidation of aniline hydrochloride with ammonium persulfate in non-aqueous media (acetone, methanol, toluene) [89]; plasma polymerization of aniline [90], photoinduced polymerization [91].

4. Preparation and properties of PANI composites with carbon nanomaterials

4.1. PANI / CNT composites

Currently, to obtain nanocomposites of PANI with carbon nanotubes, the method of oxidative polymerization of aniline on the surface of CNTs is most often used [93–99]. This is due to the fact that this approach has a number of advantages over other methods. Thus, the ability to change synthesis conditions opens up prospects for obtaining materials with specified characteristics (specific capacitance, electrical conductivity, specific surface area) for a specific field of practical application. It is also possible to implement this method on an industrial scale [92].

Studies of the morphological features of composites have shown that in composites a layer of polymer, the thickness and roughness of which is determined by the mass fraction of each component, uniformly covers the surface of the CNT [100]. It is noted that, in comparison with emeraldine, PANI deposited on the surface of CNTs has an increased content of quinonediimine fragments.

This is explained by stacking interactions between PANI and carbon nanotubes [93].

There is information about the influence of the composition of composites on their characteristics. It has been shown that PANI/CNT composites have higher electrical conductivity compared to the value of this parameter for individual components (PANI and carbon nanotubes) [49]. It has been experimentally shown that the initial PANI has the lowest electrical conductivity; with increasing CNT content in the composite, an increase in electrical conductivity is observed (Table 2). It is assumed that the increase in electrical conductivity is due to the presence of interaction between the amino groups of PANI and CNTs, which facilitates charge transfer between the polymer and carbon nanotubes [100].

Table 2. Electrical conductivity of PANI and its composites with carbon nanotubes, characterized by different mass contents of CNTs

Composite	Electrical conductivity, $\text{S}\cdot\text{cm}^{-1}$	Source
PANI/CNT (0.2 wt. %)	$0.8 \cdot 10^{-3}$	[100]
PANI/CNT (10 wt. %)	$6.6 \cdot 10^{-2}$	
PANI	$1.0 \cdot 10^{-2}$	[101]
PANI/MWCNT (0.5 wt. %)	$2.9 \cdot 10^{-1}$	
PANI/MWCNT (1 wt. %)	1.10	
PANI	0.18	[102]
PANI/MWCNT (5 wt. %)	0.85	
PANI/MWCNT (15 wt. %)	1.10	
PANI	0.17	[103]
PANI/MWCNT (0.25 wt. %)	0.22	
PANI/MWCNT (8 wt. %)	3.32	
PANI	6.25	[104]
PANI/MWCNT (5 wt. %)	17.54	
PANI/MWCNT (10 wt. %)	20.66	
PANI/MWCNT (15 wt. %)	23.10	
PANI/CNT (1 : 1)	10.00	[105]
PANI/CNT (2 : 1)	6.67	
PANI/CNT (4 : 1)	1.72	
PANI/CNT (8 : 1)	0.41	
PANI	0.028	[106]
PANI/carboxylated CNT (1 wt. %)	0.126	
PANI/carboxylated CNT (6 wt. %)	6.154	
PANI/carboxylated CNT (7 wt. %)	3.349	

Other properties of composites with PANI also depend on the CNT content. A change in the dielectric properties of the material is observed with increasing concentration of single-walled CNTs [107]. The relaxation process, analyzed using the Kohlrausch-William-Watts (KWW) model, is found to occur at lower nanofiller loadings, but gradually decays as the number of SWCNTs increases, yielding relaxation spectra that gradually resemble those of a pure conductor. In addition, the competing processes between the effects of electrical percolation and interfacial capacitance are found to be inherently dependent on the carbon filler content.

In the literature, there are few results of studies of the mechanical properties of PANI composites with carbon nanotubes. Materials testing demonstrated an increase in tensile stress by 150 % and Young's modulus by 110 % when 2 wt. % CNTs were added to the polymer [108]. Huang J. et al. report that the tensile strength of PANI/CNT film composites increases significantly to 232.3 MPa, which is more than twice the tensile strength of carbon nanomaterial (67.2 MPa). The increased tensile strength of the composites can be attributed to the interfacial adhesion between the carbon nanotube film and PANI, promoting more efficient stress transfer [109].

One way or another, obtaining a CNT dispersion is an important stage in the production of PANI/CNT nanocomposite material by chemical polymerization. As indicated in a number of studies, covalent modification of CNTs with carboxyl [110] or sulfo groups [94] allows both to ensure the dispersibility of CNTs in water and to act as a matrix for the polymerization of aniline due to interaction with the monomer and the resulting PANI. In addition, after introducing acid groups, nanotubes can act as a modifying additive for PANI, which allows polymerization to be carried out in water without adding acid. However, it should be noted that polymerization in the absence of an additional modifying additive leads to the production of a nanocomposite material with a low degree of doping and, accordingly, low conductivity (about 10^{-2} S·cm⁻¹) [94].

Pre-functionalized CNTs have been used to prepare PANI composites in other studies. Carboxylated multiwalled CNTs can be used as a dispersed carrier in a composite material demonstrating sensor sensitivity to ammonia [111]. Polyaniline was deposited onto the surface of multiwalled CNTs (MWCNTs) pre-oxidized in a mixture of nitric and sulfuric acids, and it was possible to obtain a composite with a specific surface

area of 133.55 m²·g⁻¹ and a specific capacity of 867 F·g⁻¹ [112]. Similarly prepared CNTs were used to obtain ternary CNT/PANI/ZnO composites, which have the ability to effectively absorb gamma radiation [113].

However, CNT functionalization does not always have a positive effect on the properties of composites. There are results indicating that pre-oxidation of CNTs contributes to a decrease in the conductive properties of the material [80]. There is no contradiction in these data, since most studies did not take into account the content of functional groups in CNTs. Dyachkova T.P. and colleagues were the first to analyze the influence of the method and degree of preliminary functionalization of carbon nanotubes on the process of oxidative polymerization of aniline [114]. A correlation has been established between the maximum value on the temperature curve of this reaction and the yield of its target product with the depth of preliminary oxidation of CNTs. The nature of the dependence of the electrically conductive properties of composites and the value of their specific surface area on the degree of preliminary functionalization of CNTs with carboxyl groups is shown. Composites based on carboxylated CNTs with a degree of functionalization of 0.2 mmol·g⁻¹ have the best electrical conductivity (3 S·cm⁻¹). Materials with the maximum specific surface area (more than 170 m²·g⁻¹) were obtained using CNTs oxidized with concentrated nitric acid as a substrate for the deposition of PANI.

Based on the results of calculations obtained by molecular dynamics methods, a mechanism for the modification of carboxylated CNTs with PANI was proposed [115]. It has been shown that phenazine nucleates during the oxidative polymerization of aniline are formed on the surface of nanotubes, desorbed into the bulk of the reaction mixture, where PANI macromolecules then grow.

4.2. PANI / graphene composites

Over the past decade, graphene, which consists of a single layer of sp²-hybridized carbon atoms linked into a hexagonal two-dimensional crystal lattice, has attracted enormous research attention as a functional material. This is due to its high electrical and thermal conductivity, high mechanical strength and high specific surface area [116–123]. In particular, its structure and unique electron transport properties make graphene in combination with a conducting polymer (for example, PANI) a promising material for the manufacture of electronic, electrochemical and optoelectronic devices [124–126].

Nanocomposites of PANI with graphene and its derivatives can be obtained in various ways, for example, chemical oxidative polymerization [127, 128], electrochemical oxidative polymerization [129, 130], interfacial polymerization [131], by mixing the starting components (polymer and graphene material) [132, 133].

The efficiency and simplicity of the method of chemical oxidative polymerization of aniline on the surface of graphene has made it the most common method for preparing PANI/G nanocomposites. It is reported that when using this approach to improve the electrochemical characteristics of composites and reduce the proportion of PANI in the volume of the reaction mixture, it is advisable to pre-functionalize the surface of graphene materials either with organic molecules or oxygen-containing functional groups. Thus, additional centers for polymer growth will be created on the surface of the carbon material [134]. Synthesis conditions and the percentage of polymer and carbon material in the final product affect the morphology of PANI/G composites. It has been reported that various nanostructures have been obtained: nanospheres [128], nanofibers [135, 136] or nanotubes [137].

The oxidative polymerization method can also be used to coat other carbon nanostructures, for example, mesoporous carbon, with PANI [138].

Methods for electrochemical oxidative polymerization of aniline in the presence of hafen are divided into potentiostatic [139] and potentiodynamic methods [134].

A distinctive feature of interfacial polymerization is that the aniline monomer is dissolved in organic solvents (for example, chloroform, benzene), and the oxidizing agent is dissolved in an aqueous acid solution. After transferring the prepared solutions into the reactor, an organic solvent/water interface is formed, at which the polymerization reaction occurs [131]. As a result of this approach, the PANI/G composite, which comes in the form of a composite film that can be easily separated, is formed at the interface [140].

It is also possible to obtain PANI-graphene composites by mixing and sonicating a dispersion of graphene material with previously prepared PANI [132–134]. The disadvantage of this approach is the instability of composites and their tendency to phase separation [132]. This drawback was eliminated by activating the graphene surface with the formation of acid chloride groups that interact with PANI [132–134].

4.3. Hybrid composites

In addition to binary PANI composites, the preparation of materials combining PANI, CNTs, graphene structures and other types of carbon materials has also been reported. The use of such combinations makes it possible to eliminate the disadvantages of individual dispersed carriers and, in some cases, achieve synergistic effects on various properties.

Graphene/carbon nanotubes/PANI composite can be used as a supercapacitor electrode material, which has a high specific capacitance ($1035 \text{ F}\cdot\text{g}^{-1}$) and retains up to 94 % of the original capacity after 1000 charge/discharge cycles [141].

By combining a mixture of CNTs and graphene oxide with ready-made PANI and subsequent carbonization, a composite is obtained with the specific surface $176 \text{ m}^2\cdot\text{g}^{-1}$ and the specific pore volume $0.232 \text{ cm}^3\cdot\text{g}^{-1}$ [142].

Based on PANI-modified carbon nanotubes and graphene, a mesoporous airgel with a specific surface area of $289 \text{ m}^2\cdot\text{g}^{-1}$ was obtained in a high-pressure autoclave in a supercritical isopropanol environment [143]. In this system, CNTs act as structure formers, preventing the agglomeration of graphene sheets, and PANI astices have a spherical shape. When using reduced graphene oxide and oxidized CNTs to form an airgel, it is possible to obtain a material with a higher specific surface area of $315 \text{ m}^2\cdot\text{g}^{-1}$ [144].

Natural carbon materials are often used as one of the components of hybrid composites. For example, the authors of [145] obtained a stable porous sorbent by combining PANI, multi-walled carbon nanotubes and chitosan cryogel. To obtain a flexible composite with a developed surface, porous wood was used, on the surface of which a layer of electrically conductive CNTs was deposited, after which the surface of the material was coated with PANI in situ [146]. A flexible supercapacitor based on this composite has a high specific capacity of $45.89 \text{ F}\cdot\text{g}^{-1}$ at a current of $0.2 \text{ A}\cdot\text{g}^{-1}$; after 1000 charge-discharge cycles, about 99% of the capacity is retained; in addition, even when bent by 120° , 62.9 % of capacity is retained. By introducing PANI into a conductive network based on a hybrid material “nanocellulose – multiwalled carbon nanotubes”, a film airgel electrode with a specific capacitance of the order of $2176.3 \text{ mF}\cdot\text{cm}^{-2}$ was obtained [147].

5. Application of PANI and composites based on it

PANI and its composites are of great interest for various fields of application due to the availability of fairly simple methods for their preparation and the possibility of synergistic effects when combining a dopant and PANI. Recently, most attention has been paid to the production of composites for use as electrode materials for supercapacitors, sorbents, and radiation-absorbing materials (Table 3).

As discussed above, PANI comes in a variety of forms, each with its own properties and applications. Leucoemeraldine, a fully reduced form of PANI, has found applications in electrochromic devices and lithium polymer batteries. Emeraldine salt, which is highly electrically conductive, is used in the sensor industry as an electromagnetic shielding material, in electrochromic devices, and as an electrode material in batteries. Some gas sensors are made using emeraldine salt. Pernigraniline is used in nonlinear optics [160, 161].

Composites based on PANI have high stable electrical conductivity and capacitance (up to $4800 \text{ F}\cdot\text{g}^{-1}$ [162]) (Table 4). It has also been established that the entire volume of material is involved in storing the charge. This sets this polymer apart from other conductive materials in which charge storage occurs only on the surface. Therefore, composites with PANI can be successfully used as materials for chemical current sources and supercapacitors. For these purposes, binary and three-component composites are being developed that

combine PANI, carbon nanomaterials, and metal oxides [163, 164].

The ability of PANI and composites based on it to absorb radiation (due to a combination of magnetic and dielectric properties) opens up prospects for the creation of radio-absorbing [175, 176] and electromagnetic interference shielding materials [177, 178].

PANI and materials containing it can prevent or slow down the oxidation of metal by atmospheric oxygen, which makes it possible to manufacture anti-corrosion coatings [179–181].

The possibility of using PANI in tissue engineering biosensing and targeted drug delivery has been reported [182, 183]. In addition, PANI is considered as a biocidal additive in the production of coatings that protect against viruses [184].

Moreover, composites based on PANI-modified carbon nanotubes can find wide application in electrochemical sensors, solar energy converters, and highly efficient sorbents for heavy metals, bacteria and viruses.

Let us give a number of examples. PANI/CNT composites are proposed to be used in sensors for ammonia detection [185–187]. The detection mechanism is regulated by deprotonation of the emeraldine salt of PANI by NH_3 molecules and conversion to the emeraldine base of PANI, which leads to an increase in electrical resistance. It has been shown that temperature has a strong influence on the performance of sensors. The introduction of CNTs into the composite reduces this effect.

Table 3. Application areas of composites based on PANI and carbon nanomaterials

No.	Composite	Application	Source
1	PANI/ MWCNT	Electrode materials for supercapacitors	[148]
2	PANI/G	Electrode materials for supercapacitors	[149]
3	PANI/GO/G	Electrode materials for supercapacitors	[150]
4	PANI/regenerated exhaust gas	Electrode materials for supercapacitors	[151]
5	PANI/porous carbon microspheres	Electrode materials for supercapacitors	[152]
6	PANI/GO PANI/CNT	Sorbents	[153]
7	PANI/GO/CNT	Sorbents	[154]
8	PANI/regenerated exhaust gas	Sensors for temperature, relative humidity, pesticide detection	[155]
9	PANI/carboxylated CNTs	Biosensors	[156]
10	PANI/ MWCNT/ STARCH	Biosensors	[157]
11	PANI/CNT/Gold nanoparticles	Sensors for detecting zinc, lead and copper	[158]
12	PANI/CNT	Microwave absorbing materials	[159]

Table 4. Specific capacity and stability of PANI and its composites

No.	Composite	Specific capacitance, $F \cdot g^{-1}$	Current ($A \cdot g^{-1}$) or scan rate ($mV \cdot s^{-1}$)	Capacitance conservation	Source
1	PANI/CNT/MoS ₂	350	10 $A \cdot g^{-1}$	68 % after 2000 cycles	[165]
2	PANI/GO/MoS ₂	815	10 $mV \cdot s^{-1}$	93 % after 100 cycles	[166]
3	PANI/GO/TiO ₂	713	10 $mV \cdot s^{-1}$	94 % after 100 cycles	
4	MWCNT	30	0.4 $A \cdot g^{-1}$	–	[167]
5	PANI	210	0.4 $A \cdot g^{-1}$	–	
6	PANI/MWCNT/TiO ₂	270	0.4 $A \cdot g^{-1}$	67 % after 6000 cycles	
7	PANI/MWCNT/Ni(OH) ₂	1917	1.0 $A \cdot g^{-1}$	75 % after 1000 cycles	[168]
8	PANI/polyndol (2:1)	682.4	0.5 $A \cdot g^{-1}$	78.6 % after 1000 cycles	[169]
9	PANI/polyndole/MWCNT (3 wt. %)	895	0.5 $A \cdot g^{-1}$	97.8 % after 1000 cycles	
10	PANI/CNT/graphene	415	3 $A \cdot g^{-1}$	96 % after 5000 cycles	[170]
11	PANI/graphene	310	3	74 % after 5000 cycles	
12	PANI/CNT	215	3	84 % after 5000 cycles	
13	PANI/reduced GO/Fe ₃ O ₄	486.5	1	52.1 % after 2000 cycles	[171]
14	PANI/sulfonated graphene/NiO	1350	1	92.23 % after 5000 cycles	[172]
15	PANI/GO/MWCNT	696	20 $mV \cdot s^{-1}$	–	[173]
16	PANI/GO/CoFe ₂ O ₄	781.27	1 $mV \cdot s^{-1}$	79.03 % after 5000 cycles	[174]

PANI composites with reduced graphene oxide have been used to fabricate a VOC sensor that exhibits high sensitivity towards methanol gas [188]. To detect nitrite in tap and rain water, an electrode modified with a reduced graphene oxide/MnFe₂O₄/PANI composite was developed [189].

Electrically conductive PANI/CNT composites have found application in the creation of various electrochemical enzyme sensors: sensors for the detection of ascorbic acid [190], glucose [191], phenolic compounds [192], pesticides [193], and cholesterol [194]. A sensor based on PANI and graphene oxide was developed to determine cortisol in human saliva [195].

The possibility of using PANI/CNT composites in solar cells was studied [196, 197]. It was shown that the performance of solar cells increases as a result of using a PANI/CNT composite. The increase in conversion efficiency is explained by more efficient charge transfer due to suppression of the charge recombination process [198].

Composite adsorbents consisting of PANI and carbon nanomaterials are increasingly considered as promising materials for water purification due to their ability to sorb various types of pollutants [199–201]. The prospects for using PANI as an adsorbent are due to the presence of adsorption

centers, which are amine and imine groups that interact with pollutants in aqueous solutions [202].

It was shown that PANI/CNT composites can be used for the sorption of copper and nickel ions from water [203]. At the same time, deprotonation of PANI has little effect on this process, and the conversion of the modifying layer of PANI into the leucobase form upon reduction with hydrazine sharply increases the sorption capacity of the material for copper ions. PANI/CNT and PANI/GNP composites can be used for the sorption of various pollutants and pathogenic microorganisms [204], and the successful use of PANI/CNT composites for the extraction of scandium ions from aqueous media has been reported [205].

Hybrid composites based on mixtures of CNTs and graphene materials embedded with PANI demonstrate high sorption capacity with respect to zinc ions (346 $mg \cdot g^{-1}$ at pH 6.5) [142] and lead (350 $mg \cdot g^{-1}$) [143] and others heavy metals [144].

Some sources report quite unusual applications of PANI-based composites. PANI-modified graphene nanoplatelets were used as a reinforcing filler for a composite based on highly oriented ultra-high molecular weight polyethylene (UHMWPE) [206, 207]. It was found that PANI helps to reduce the aggregation of GNP in the polymer matrix and

increase the degree of its crystallinity. The new lamellar crystal structure has high stretchability. The highest tensile strength of 1330 MPa has a composite containing 2 wt. % GNP/PANI filler, and the highest value of Young's modulus of 41 GPa is observed at 1 % content of the modified filler.

6. Conclusion

In this review, we have shown the promise of using PANI and its composites with carbon nanomaterials in various industries due to their unique electrical, physical, chemical, and optical properties. Recent studies show that combining PANI with various substances (carbon nanotubes, graphene, graphene oxide, metal oxides) can improve the performance characteristics of the polymer.

However, despite numerous studies and positive results, many challenges still need to be overcome on the path to commercialization of composites. The analyzed studies are devoted to the development of new materials of complex composition, the study of their properties, and specific proposals for practical use.

A generalization of scientific results shows that the selection of the optimal composition of composites remains relevant in order to find ways to increase their electrical capacity and cyclic stability, increase electrical conductivity and specific surface area. For this purpose, materials are developed that consist of three or more components. And obviously, by varying their mass ratio, fundamentally different materials can be obtained. It has been shown that the properties of composites with PANI depend on the presence of functional groups on the CNM surface. Although such information is available in the literature, it is scattered and requires additional study.

It is assumed that in the near future, composites being developed with PANI may become the basis of many technologies that provide a high-quality standard of living (ecology, energy, safety), but for this it is necessary to continue scientific research. Thus, it is necessary to establish what effect functional groups on the surface of carbon nanomaterials have on the performance characteristics of composites. To evaluate the effectiveness of composites, it is necessary to test them in practice, and for further commercialization it is necessary to develop protocols/recommendations that include a description of methods for obtaining composites with a given structure and properties.

7. Funding

This study received no external funding.

8. Conflict of interests

The authors declare no conflict of interests.

References

1. Li Z, Gong L. Research progress on applications of polyaniline (PANI) for electrochemical energy storage and conversion. *Materials*. 2020;13(3):548. DOI:10.3390/ma13030548
2. Thambidurai S, Pandiselvi K. Polyaniline/natural polymer composites and nanocomposites. In: Visakh PM, Pina CD, Falletta E. (eds.) *Polyaniline blends, composites, and nanocomposites*. Elsevier; 2018, p.235-256. DOI:10.1016/b978-0-12-809551-5.00009-6
3. Stejskal J, Gilbert RG. Polyaniline. Preparation of a conducting polymer (IUPAC Technical Report). *Pure and Applied Chemistry*. 2002;74(5):857-867. DOI:10.1351/pac200274050857
4. Chiang JC, MacDiarmid AG. «Polyaniline»: Protonic acid doping of the emeraldine form to the metallic regime. *Synthetic Metals*. 1986;13(1-3):193-205. DOI:10.1016/0379-6779(86)90070-6
5. Zhang P, Zhai X, Huang H, et al. Capacitance fading mechanism and structural evolution of conductive polyaniline in electrochemical supercapacitor. *Journal of Materials Science: Materials in Electronics*. 2020;31; 14625-14634. DOI:10.1007/s10854-020-04025-y
6. Pawar DC, Malavekar DB, Lokhande AC, et al. Facile synthesis of layered reduced graphene oxide/polyaniline (rGO/PANI) composite electrode for flexible asymmetric solid-state supercapacitor. *Journal of Energy Storage*. 2024;79:110154. DOI:10.1016/j.est.2023.110154
7. Yang J, Liu Y, Liu S, et al. Conducting polymer composites: material synthesis and applications in electrochemical capacitive energy storage. *Materials Chemistry Frontiers*. 2017;1(2):251-268. DOI:10.1039/C6QM00150E
8. Che B, Li H, Zhou D, et al. Porous polyaniline/carbon nanotube composite electrode for supercapacitors with outstanding rate capability and cyclic stability. *Composites Part B: Engineering*. 2019;165:671-678. DOI:10.1016/j.compositesb.2019.02.026
9. Liao G, Li Q, Xu Z. The chemical modification of polyaniline with enhanced properties: A review. *Progress in Organic Coatings*. 2019;126:35-43. DOI:10.1016/j.porgcoat.2018.10.018
10. Nezakati T, Seifalian A, Tan A, et al. Conductive polymers: opportunities and challenges in biomedical applications. *Chemical Reviews*. 2018;118:6766-6843. DOI:10.1021/acs.chemrev.6b00275
11. Runge FF. Über einige Produkte der Steinkohlendestillation. *Annalen der Physik*. 1834;107(5): 65-78.
12. Fritzsche J. Ueber das Anilin, ein neues Zersetzungsproduct des Indigo. *Journal für Praktische Chemie*. 1840;20(1):453-459.
13. Fritzsche J. Vorläufige Notiz über einige neue Körper aus der Indigoreihe. *Journal für Praktische Chemie*. 1843;28(1):198-204.

14. Letheby H. On the production of a blue substance by the electrolysis of sulphate of aniline. *Journal of the Chemical Society*. 1862;15:161-163. DOI:10.1039/JS8621500161
15. Ciric-Marjanovic G. Recent advances in polyaniline research: Polymerization mechanisms, structural aspects, properties and applications. *Synthetic Metals*. 2013;177:1-47. DOI:10.1016/j.synthmet.2013.06.004
16. Abe M, Ohtani A, Umemoto Y, et al. Soluble and high molecular weight polyaniline. *Journal of the Chemical Society, Chemical Communications*. 1989;(22):1736-1738. DOI:10.1039/c39890001736
17. Jozefowicz M, Yu LT, Perichon J, et al. Proprietes nouvelles des polymeres semiconducteurs. *Journal of Polymer Science: Part C*. 1969;22:1187-1195. DOI:10.1002/polc.5070220251
18. MacDiarmid AG, Chiang JC, Halpern M, et al. «Polyaniline»: Interconversion of Metallic and Insulating Forms. *Molecular Crystals and Liquid Crystals*. 1985;121:173-180. DOI:10.1080/00268948508074857
19. Do Nascimento GM. Spectroscopy of Polyaniline Nanofibers. In: *Nanofibers*. In Tech; 2010. DOI:10.5772/8162
20. Goswami S, Nandy S, Fortunato E, et al. Polyaniline and its composites engineering: A class of multifunctional smart energy materials. *Journal of Solid State Chemistry*. 2023;317(A):123679. DOI:10.1016/j.jssc.2022.123679
21. Jangid NK, Jadoun S, Kaur N. A review on high-throughput synthesis, deposition of thin films and properties of polyaniline. *European Polymer Journal*. *European Polymer Journal*. 2020;125:109485. DOI:10.1016/j.eurpolymj.2020.109485
22. Gospodinova N, Terlemezyan L. Conducting polymers prepared by oxidative polymerization: polyaniline. *Progress in Polymer Science*. 1998;23(8):1443-1484. DOI:10.1016/s0079-6700(98)00008-2
23. Sun P, Shen X, Xu P, et al. Conductive polyaniline film synthesized through in-situ polymerization as a conductive seed layer for hole metallization of printed circuit boards. *Applied Surface Science*. 2024;655:159649. DOI:10.1016/j.apsusc.2024.159649
24. Ležaić AJ, Bajuk-Bogdanović D, Ćirić-Marjanović G. In situ Raman spectroscopy study of the oxidative polymerization of aniline in media of different acidity. *Synthetic Metals*. 2024;305:117602. DOI:10.1016/j.synthmet.2024.117602
25. Hussain AMP, Kumar A. Electrochemical synthesis and characterization of chloride doped polyaniline. *Bulletin of Materials Science*. 2003;20:329-344. DOI:10.1007/BF02707455
26. Shan J, Han L, Bai F, et al. Enzymatic polymerization of aniline and phenol derivatives catalyzed by horseradish peroxidase in dioxane(II). *Polymers for Advanced Technologies*. 2003;14(3-5):330-336. DOI:10.1002/pat.316
27. Mohammad RS, Zarrintaj P, Khandelwal P, et al. Synthetic route of polyaniline (I): Conventional oxidative polymerization. In: Mozafari M, Chauhan NPS (eds.) *Fundamentals and Emerging Applications of Polyaniline*, Elsevier, 2019. p. 17-41. DOI:10.1016/B978-0-12-817915-4.00002-6
28. Yılmaz F, Küçükyavuz Z. The influence of polymerization temperature on structure and properties of polyaniline. *e-Polymers*. 2009;9(1). DOI:10.1515/epoly.2009.9.1.48
29. Tran HD, D'Arcy JM, Wang Y, et al. The oxidation of aniline to produce “polyaniline”: a process yielding many different nanoscale structures. *Journal of materials Chemistry*. 2011;21:3534-3550. DOI:10.1039/c0jm02699a
30. Stejskal J, Sapurina I, Trchová M. Polyaniline nanostructures and the role of aniline oligomers in their formation. *Progress in Polymer Science*. 2010; 35(12):1420-1481. DOI:10.1016/j.progpolymsci.2010.07.006
31. Trchová M, Konyushenko EN, Stejskal J, et al. The conversion of polyaniline nanotubes to nitrogen-containing carbon nanotubes and their comparison with multi-walled carbon nanotubes. *Polymer Degradation and Stability*. 2009;94(6):929-938. DOI:10.1016/j.polymdegradstab.2009.03.001
32. Dhawale DS, Dubal DP, Jamadade VS, et al. Fuzzy nanofibrous network of polyaniline electrode for supercapacitor application. *Synthetic Metals*. 2010;160:519-522. DOI: 10.1016/j.synthmet.2010.01.021
33. Mandić Z, Roković MK, Pokupčić T. Polyaniline as cathodic material for electrochemical energy sources. The role of morphology. *Electrochimica Acta*. 2009; 54(10):2941-2950. DOI:10.1016/j.electacta.2008.11.002
34. Qin Q, Tao J, Yang Y. Preparation and characterization of polyaniline film on stainless steel by electrochemical polymerization as a counter electrode of DSSC. *Synthetic Metals*. 2010;160(11-12):1167-1172. DOI: 10.1016/j.synthmet.2010.03.003
35. Lukachova. LV, Shkerin EA, Puganova EA, et al. Electroactivity of chemically synthesized polyaniline in neutral and alkaline aqueous solutions. *Journal of Electroanalytical Chemistry*. 2003;544:59-63. DOI:10.1016/s0022-0728(03)00065-2
36. Sayah A, Habelhames F, Bennouioua A, et al. Capacitance of polyaniline films synthesized by direct and pulse potentiostatic methods. *Journal Marocain de Chimie Hétérocyclique*. 2021;20(2):108-116. DOI:10.48369/IMIST.PRSM/jmch-v20i2.24711
37. Gojgić J, Petrović M, Jugović B, et al. Electrochemical and electrical performances of high energy storage polyaniline electrode with supercapattery behavior. *Polymers*. 2022;14(24):5365. DOI:10.3390/polym14245365
38. Duić L, Mandić Z. Counter-ion and pH effect on the electrochemical synthesis of polyaniline. *Journal of Electroanalytical Chemistry*. 1992;335(1-2):207-221. DOI:10.1016/0022-0728(92)80243-W
39. Abalyaeva VV, Kogan IL. Initiating agents for electrochemical polymerization of aniline on titanium electrodes. *Synthetic Metals*. 1994;63(2):109-113. DOI:10.1016/0379-6779(94)90257-7
40. Lee HT, Chuang KR, Chen SA, et al. Conductivity relaxation of 1-methyl-2-pyrrolidone-

- plasticized polyaniline film. *Macromolecules*. 1995; 28:7645-7652. DOI:10.1021/ma00127a009
41. Dhawale DS, Salunkhe RR, Jamadade VS, et al. Hydrophilic polyaniline nanofibrous architecture using electrosynthesis method for supercapacitor application. *Current Applied Physics*. 2010;10(3):904-909. DOI:10.1016/j.cap.2009.10.020
42. Zhang H, Wang J, Wang Z, et al. Electrodeposition of polyaniline nanostructures: A lamellar structure. *Synthetic Metals*. 2009;159(3-4):277-281. DOI:10.1016/j.synthmet.2008.09.015
43. Zhao L, Li X-X, Guo Y-X, et al. Electrochemical Polymerization and Characterization of Polyaniline/Carbon Nanotube Composite Films. *Proceedings of the 2nd Annual International Conference on Advanced Material Engineering (AME 2016)*. 2016;281-286. DOI:10.2991/ame-16.2016.47
44. Itoi H, Hayashi S, Matsufusa H, et al. Electrochemical synthesis of polyaniline in the micropores of activated carbon for high-performance electrochemical capacitors. *Chemical Communications*. 2017;53:3201-3204. DOI:10.1039/C6CC08822H
45. Blinova NV, Stejskal J, Trchová M, et al. Polyaniline prepared in solutions of phosphoric acid: Powders, thin films, and colloidal dispersions. *Polymer*. 2006;47:42-48. DOI:10.1016/j.polymer.2005.10.145
46. Konyushenko EN, Stejskal J, Trchová M, et al. Multi-wall carbon nanotubes coated with polyaniline. *Polymer*. 2006;47(16):5715-5723. DOI:10.1016/j.polymer.2006.05.059
47. Konyushenko EN, Stejskal J, Šeděnková I, et al. Polyaniline nanotubes: Conditions of formation. *Polymer International*. 2006;55(1):31-39. DOI:10.1002/pi.1899
48. Stejskal J, Sapurina I, Trchová M, et al. The genesis of polyaniline nanotubes. *Polymer*. 2006;47:8253-8262. DOI:10.1016/j.polymer.2006.10.007
49. Stejskal J, Sapurina I, Trchová M, et al. Oxidation of aniline: Polyaniline granules, nanotubes, and oligoaniline microspheres. *Macromolecules*. 2008;41(10):3530-3536. DOI:10.1021/ma702601q
50. Ding H, Shen J, Wan M, et al. Formation mechanism of polyaniline nanotubes by a simplified template-free method. *Macromolecular Chemistry and Physics*. 2008;209(8):864-871. DOI:10.1002/macp.200700624
51. Zhang L, Zujovic ZD, Peng H, et al. Structural characteristics of polyaniline nanotubes synthesized from different buffer solutions. *Macromolecules*. 2008;41:8877-8884. DOI:10.1021/ma801728j
52. Wang J, Zhang D. One-dimensional nanostructured polyaniline: syntheses, morphology controlling, formation mechanisms, new features, and applications. *Advances in Polymer Technology*. 2012;32:E323-E368. DOI:10.1002/adv.21283
53. Anju C, Palatty Sh. Ternary doped polyaniline-metal nanocomposite as high performance supercapacitive material. *Electrochimica Acta*. 2019;299:626-635. DOI:10.1016/j.electacta.2019.01.030
54. Lin K, Hu L, Chen K, et al. Characterization of polyaniline synthesized from chemical oxidative polymerization at various polymerization temperatures. *European Polymer Journal*. 2017;88:311-319. DOI:10.1016/j.eurpolymj.2017.01.035
55. Yashwanth VN, Kariduraganavar MY, Srinivasa HT, et al. Synthesis and characterization of cotton candy-PANI: Enhanced supercapacitance properties. *Journal of the Indian Chemical Society*. 2023;100(3):100944. DOI:10.1016/j.jics.2023.100944
56. Prasutiyo YJ, Manaf A, Hafizah MAE. Synthesis of polyaniline by chemical oxidative polymerization and characteristic of conductivity and reflection for various strong acid dopants. *Journal of Physics: Conference Series*. 2020;1442:012003. DOI:10.1088/1742-6596/1442/1/012003
57. Shaari HAH, Mohtar MN, Rahman NA, et al. Synthesis and functional characterization of conducting polyaniline by oxidative polymerization method. *AIP Conference Proceedings*. 2022;2506(1):030001. DOI:10.1063/5.0084374
58. Zeng F, Qin Z, Liang B, et al. Polyaniline nanostructures tuning with oxidants in interfacial polymerization system. *Progress in Natural Science: Materials International*. 2015;25(5):512-519. DOI:10.1016/j.pnsc.2015.10.002
59. Yasuda A, Shimidzu T. Chemical oxidative polymerization of aniline with ferric chloride. *Polymer Journal*. 1993;25(4):329-338. DOI:10.1295/polymj.25.329
60. Lyu W, Yu M, Li J, et al. Adsorption of anionic acid red G dye on polyaniline nanofibers synthesized by FeCl₃ oxidant: Unravelling the role of synthetic conditions. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*. 2022;647:129203. DOI:10.1016/j.colsurfa.2022.129203
61. Bláha M, Riesová M, Zedník J. Polyaniline synthesis with iron (III) chloride – hydrogen peroxide catalyst system: Reaction course and polymer structure study. *Synthetic Metals*. 2011;161:1217-1225. DOI:10.1016/j.synthmet.2011.04.008
62. Ayad M, Amer W, Whdan M. In situ polyaniline film formation using ferric chloride as an oxidant. *Journal of Applied Polymer Science*. 2012;125:2695-2700. DOI:10.1002/app.36584
63. Chiolerio A, Bocchini S, Crepaldi M, et al. Bridging electrochemical and electron devices: fast resistive switching based on polyaniline from one pot synthesis using FeCl₃ as oxidant and co-doping agent. *Synthetic Metals*. 2017;229:72-81. DOI:10.1016/j.synthmet.2017.05.001
64. Nestorović GD, Jeremić KB, Jovanović SM. Kinetics of aniline polymerization initiated with iron (III) chloride. *Journal of the Serbian Chemical Society*. 2006;71:895-904. DOI:10.2298/JSC0609895N
65. Yan H, Kajita M, Toshima N. Polymerization of aniline using iron(III) catalyst and ozone, and kinetics of oxidation reactions in the catalytic system. *Macromolecular Materials and Engineering*. 2002;287(8):503-508. DOI:10.1002/1439-2054(20020801)287:8<503::aid-mame503>3.0.co;2-n
66. Syed AA, Dinesan MK. Review: Polyaniline – A novel polymeric material. *Talanta*. 1991;38(8):815-837. DOI:10.1016/0039-9140(91)80261-w

67. Cao Y, Andreatta A, Heeger AJ, et al. Influence of chemical polymerization conditions on the properties of polyaniline. *Polymer*. 1989;30(12):2305-2311. DOI:10.1016/0032-3861(89)90266-8
68. Jun TS, Kim CK, Kim YS. Vapor phase polymerization of polyaniline nanotubes using Mn₃O₄ nanofibers as an oxidant. *Materials Letters*. 2014;133:17-19. DOI:10.1016/j.matlet.2014.06.154
69. Li Y, Gong J, He G, et al. Fabrication of polyaniline / titanium dioxide composite nanofibers for gas sensing application. *Materials Chemistry and Physics*. 2011;129(1-2):477-482. DOI:10.1016/j.matchemphys.2011.04.045
70. Fei J, Cui Y, Yan X, et al. Controlled fabrication of polyaniline spherical and cubic shells with hierarchical nanostructures. *ACS Nano*. 2009;3(11):3714-3718. DOI:10.1021/nn900921v
71. Yakubu A, Monday M, Tsado MJ, et al. In situ synthesis of polyaniline nanohybrid and formulation of polyaniline/carboxymethyl cellulose/ethylene glycol nanocomposite: study of its conducting and antibacterial properties. *Journal of Materials and Polymer Science*. 2023;3(4):1-9. DOI:10.47485/2832-9384.1041
72. Bláha M, Trchová M, Bober P, et al. Polyaniline: Aniline oxidation with strong and weak oxidants under various acidity. *Materials Chemistry and Physics*. 2017;194:206-218. DOI:10.1016/j.matchemphys.2017.03.028
73. Ullah R, Bowmaker GA, Laslau C, et al. Synthesis of polyaniline by using CuCl₂ as oxidizing agent. *Synthetic Metals*. 2014;198:203-211. DOI:10.1016/j.synthmet.2014.10.005
74. Chuanyu S, Yu W. Synthesis of polyaniline nanotubes through UV light catalytic method. *Materials Science-Poland*. 2015;33(1):193-197. DOI:10.1515/msp-2015-0022
75. Jangid NK, Jadoun S, Kaur N. A Review on high-throughput synthesis, deposition of thin films and properties of polyaniline. *European Polymer Journal*. 2020;125:109485. DOI:10.1016/j.eurpolymj.2020.109485
76. Powar K, Vengurlekar P. Applications of electroactive polymer in electronics and Mechatronics. *International Journal of Scientific & Engineering Research*. 2018;9(2):21-34.
77. Ćirić-Marjanović G. Recent advances in polyaniline composites with metals, metalloids and nonmetals. *Synthetic Metals*. 2013;170(1):31-56. DOI:10.1016/j.synthmet.2013.02.028
78. Gu Y, Tsai JY. Enzymatic synthesis of conductive polyaniline in the presence of ionic liquid. *Synthetic Metals*. 2012;161(23-24):2743-2747. DOI:10.1016/j.synthmet.2011.10.013
79. Guo Z, Hauser N, Moreno A, et al. AOT vesicles as templates for the horseradish peroxidase-triggered polymerization of aniline. *Soft Matter*. 2011;7:180-193. DOI:10.1039/C0SM00599A
80. Ding Q, Qian R, Jing X, et al. Reaction of aniline with KMnO₄ to synthesize polyaniline-supported Mn nanocomposites: An unexpected heterogeneous free radical scavenger. *Materials Letters*. 2019;251:222-225. DOI:10.1016/j.matlet.2019.05.076
81. Dyachkova TP, Melezhyk AV, Morozova Zh.G, et al. Effect of the nature of oxidant and synthesis conditions on properties of nanocomposites polyaniline/carbon nanotubes. *Vestnik Tambovskogo gosudarstvennogo tekhnicheskogo universiteta*. 2012;18(3):718-730. (In Russ.)
82. Bláha M, Zedník J, Vohlídal J. Self-doping of polyaniline prepared with the FeCl₃/H₂O₂ system and the origin of the Raman band of emeraldine salt at around 1375 cm⁻¹. *Polymer International*. 2015;64(12):1801-1807. DOI:10.1002/pi.4983
83. Garcia-Bernabé A, Gil-Agustí M, Ortega G, et al. On the effect of the oxidative reagents on the conductivity of polyaniline/MMT nanocomposites. *AIP Conference Proceedings*. 2010;1255:273-275. DOI:10.1063/1.3455605
84. Majeed A, Mohammed L, Hammoodi O, et al. A review on polyaniline: synthesis, properties, nanocomposites, and electrochemical applications. *International Journal of Polymer Science*. 2022;2022:9047554. DOI:10.1155/2022/9047554
85. Carrillo N, León-Silva U, Avalos T, et al. Enzymatically synthesized polyaniline film deposition studied by simultaneous open circuit potential and electrochemical quartz crystal microbalance measurements. *Journal of Colloid and Interface Science*. 2012;369(1):103-110. DOI:10.1016/j.jcis.2011.12.021
86. Felix JF, Barros RA, M. de Azevedo W, et al. X-ray irradiation: A non-conventional route for the synthesis of conducting polymers. *Synthetic Metals*. 2011;161:173-176. DOI:10.1016/j.synthmet.2010.11.017
87. Park JK, Kwon OP, Choi EY, et al. Enhanced electrical conductivity of polyaniline film by a low magnetic field. *Synthetic Metals*. 2010;160:728-731. DOI:10.1016/j.synthmet.2010.01.011
88. Jackowska K, Bieguński AT, Tagowska M. Hard template synthesis of conducting polymers: A route to achieve nanostructures. *Journal of Solid State Electrochemistry*. 2008;12(4):437-443. DOI:10.1007/s10008-007-0453-7
89. Konyushenko EN, Stejskal J, Trchová M, et al. Suspension polymerization of aniline hydrochloride in non-aqueous media. *Polymer International*. 2011;60(5):794-797. DOI:10.1002/pi.3017
90. Kim JY, Jang H, Lee YR, et al. Nanostructured polyaniline films functionalized through auxiliary nitrogen addition in atmospheric pressure plasma polymerization. *Polymers*. 2023;15(7):1626. DOI:10.3390/polym15071626
91. Sury S, Ulianas A, Aini S. Synthesis of conducting polyaniline with photopolymerization method and characterization. *Journal of Physics: Conference Series*. 2020;1788:012004. DOI:10.1088/1742-6596/1788/1/012004
92. Stejskal J, Riede A, Hlavatá D, et al. The effect of polymerization temperature on molecular weight, crystallinity, and electrical conductivity of polyaniline. *Synthetic Metals*. 1998;96:55-61. DOI:10.1016/S0379-6779(98)00064-2

93. Adams PM, Abell L, Middleton A, et al. Low temperature synthesis of high molecular weight polyaniline using dichromate oxidant. *Synthetic Metals*. 1997;84(1-3):61-62. DOI:10.1016/s0379-6779(96)03836-2
94. Peng C, Zhang S, Jewell D, et al. Carbon nanotube and conducting polymer composites for supercapacitors. *Progress in Natural Science*. 2008;18(7):777-788. DOI:10.1016/j.pnsc.2008.03.002
95. Wu G, Du H, Cha YL, et al. A wearable mask sensor based on polyaniline/CNT nanocomposites for monitoring ammonia gas and human breathing. *Sensors and Actuators B: Chemical*. 2023;375:132858. DOI:10.1016/j.snb.2022.132858
96. Rodrigues de Souza VH, Oliveira M, Zarbin AJ. Thin and flexible all-solid supercapacitor prepared from novel single wall carbon nanotubes/polyaniline thin films obtained in liquid-liquid interfaces. *Journal of Power Sources*. 2014;260:34-42. DOI:10.1016/j.jpowsour.2014.02.070
97. Yoo R, Kim J, Song M-J, et al. Nano-composite sensors composed of single-walled carbon nanotubes and polyaniline for the detection of a nerve agent simulant gas. *Sensors and Actuators B: Chemical*. 2015;209:444-448. DOI:10.1016/j.snb.2014.11.137
98. Abdulla S, Lazar T, Pullithadathil M. Highly sensitive, room temperature gas sensor based on polyaniline-multiwalled carbon nanotubes (PANI/MWCNTs) nanocomposite for trace-level ammonia detection. *Sensors and Actuators B: Chemical*. 2015;21:1523-1534. DOI:10.1016/j.snb.2015.08.002
99. Wang Y, Zhang S, Deng Y. Semiconductor to metallic behavior transition in multi-wall carbon nanotubes/polyaniline composites with improved thermoelectric properties. *Materials Letters*. 2016;164:132-135. DOI:10.1016/j.matlet.2015.10.138
100. Oueiny C, Berlioz S, Perrin F.-X. Carbon nanotube-polyaniline composites. *Progress in Polymer Science*. 2014;39(4):707-748. DOI:10.1016/j.progpolymsci.2013.08.009
101. Wang Q, Qian X, Wang S, et al. Conductive polyaniline composite films from aqueous dispersion: Performance enhancement by multi-walled carbon nanotube. *Synthetic Metals*. 2015;199:1-7. DOI:10.1016/j.synthmet.2014.11.007
102. Tan H, Xu X. Conductive properties and mechanism of various polymers doped with carbon nanotube/polyaniline hybrid nanoparticles. *Composites Science and Technology*. 2016;128:155-160. DOI:10.1016/j.compscitech.2016.03.027
103. Bachhav SG, Patil DR. Synthesis and characterization of polyaniline-multiwalled carbon nanotube nanocomposites and its electrical percolation behavior. *American Journal of Materials Science*. 2015;5(4):90-95. DOI:10.5923/j.materials.20150504.03
104. Xavier PAF, Benoy MD, Stephen SK, et al. Enhanced electrical properties of polyaniline carbon nanotube composites: Analysis of temperature dependence of electrical conductivity using variable range hopping and fluctuation induced tunneling models. *Journal of Solid State Chemistry*. 2021;300:122232. DOI:10.1016/j.jssc.2021.122232
105. Zhang J, Zhu A. Study on the synthesis of PANI/CNT nanocomposite and its anticorrosion mechanism in waterborne coatings. *Progress in Organic Coatings*. 2021;159:106447. DOI:10.1016/j.porgcoat.2021.106447
106. Bora A, Mohan K, Pegu D, et al. A room temperature methanol vapor sensor based on highly conducting carboxylated multi-walled carbon nanotube/polyaniline nanotube composite. *Sensors and Actuators B: Chemical*. 2017;253:977-986. DOI:10.1016/j.snb.2017.07.023
107. Islam R, Papathanassiou A, Chan-Yu-King R, et al. Competing charge trapping and percolation in core-shell single wall carbon nanotubes/polyaniline nanostructured composites. *Synthetic Metals*. 2020;259:116259. DOI:10.1016/j.synthmet.2019.116259
108. Mottaghitalab V, Spinks GM, Wallace GG. The influence of carbon nanotubes on mechanical and electrical properties of polyaniline fibers. *Synthetic Metals*. 2005;152(1-3):77-80. DOI:10.1016/j.synthmet.2005.07.154
109. Huang J, Liu X, Du Y. Highly efficient and wearable thermoelectric composites based on carbon nanotube film/polyaniline. *Journal of Materiomics*. 2024;10(1):173-178. DOI:10.1016/j.jmat.2023.04.014
110. Wu T.-M, Lin Y.-W. Doped polyaniline/multi-walled carbon nanotube composites: Preparation, characterization and properties. *Polymer*. 2006;47(10):3576-3582. DOI:10.1016/j.polymer.2006.03
111. Snook GA, Kao P, Best AS. Conducting-polymer-based supercapacitor devices and electrodes. *Journal of Power Sources*. 2011;196(1):1-12. DOI:10.1016/j.jpowsour.2010
112. Singh G, Kumar Y, Husain S. Fabrication of high energy density symmetric polyaniline/functionalized multiwalled carbon nanotubes supercapacitor device with swift charge transport in different electrolytic mediums. *Journal of Energy Storage*. 2023;65. DOI:10.1016/j.est.2023.107328
113. Ali ES, Issa Sh, Zakaly H, et al. Exploration of optical and gamma radiation shielding characteristics of zinc oxide nanoparticles doped functionalized multi-walled carbon nanotubes nanohybrids based polyaniline ternary nanocomposites. *Diamond and Related Materials*. 2024;143:110882. DOI:10.1016/j.diamond.2024.110882
114. Dyachkova TP, Anosova IV, Tkachev AG, et al. Synthesis of composites from functionalized carbon nanotubes and polyaniline. *Inorganic Materials: Applied Research*. 2018;9(2):305-310. DOI:10.1134/S2075113318020089
115. Gutnik IV, Dyachkova TP, Rukhov AV, et al. Polyaniline/carbon nanotubes composites: kinetic laws of synthesis, morphology and properties. *Advanced Materials and Technologies*. 2018;4:54-68. DOI:10.17277/amt.2018.04.pp.054-068

116. Geim AK, Novoselov KS. The rise of grapheme. *Nature Materials*. 2007;6(3):183-191. DOI:10.1038/nmat1849
117. Mehmooda Ah, Mubarak NM, Khalidb M, et al. Graphene based nanomaterials for strain sensor application – a review. *Journal of Environmental Chemical Engineering*. 2020;8:103743. DOI:10.1016/j.jece.2020.103743
118. Yang Y, Wei Y, Guo Z, et al. From materials to devices: graphene toward practical applications (Review). *Small Methods*. 2022;6(10):2200671. DOI:10.1002/smtd.202200671
119. Sahoo PK, Kumar N, Jena A, et al. Recent progress in graphene and its derived hybrid materials for high-performance supercapacitor electrode applications. *RSC Advances*. 2024;14(2):1284-1303. DOI:10.1039/d3ra06904d
120. Avinash K, Patolsky F. Laser-induced graphene structures: From synthesis and applications to future prospects. *Materials Today*. 2023;70:104-136. DOI:10.1016/j.mattod.2023.10.009
121. Nair AS, Sreejakumari SS, Venkatesan J, et al. A novel top-down approach for high yield production of graphene from natural graphite and its supercapacitor applications. *Diamond and Related Materials*. 2024;144:111025. DOI:10.1016/j.diamond.2024.111025
122. Ahmad F, Ghazal H, Rasheed F, et al. Graphene and its derivatives in medical applications: A comprehensive review. *Synthetic Metals*. 2024;304:117594. DOI:10.1016/j.synthmet.2024.117594
123. Nam J, Yang J, Zhao Y, et al. Chemical vapor deposition of graphene and its characterizations and applications. *Current Applied Physics*. 2024;61:55-70. DOI:10.1016/j.cap.2024.02.010
124. Prasannakumar AT, Rohith R, Manju V, et al. Graphene nanoflake-self stabilized dispersion polymerized PANI hybrids as efficient, binder-free electrode materials for high-performance flexible symmetric supercapacitors. *Journal of Electroanalytical Chemistry*. 2024;952:117952. DOI:10.1016/j.jelechem.2023.117952
125. Kerli S, Bhardwaj S, Lin W, et al. Silver-doped reduced graphene oxide/PANI composite synthesis and their supercapacitor applications. *Journal of Organometallic Chemistry*. 2023;995:122725. DOI:10.1016/j.jorgchem.2023.122725
126. Kenesi AG, Ghorbani M, Lashkenari MS. High electrochemical performance of PANI/CdO nanocomposite based on graphene oxide as a hybrid electrode materials for supercapacitor application. *International Journal of Hydrogen Energy*. 2022;47(91):38849-38861. DOI:10.1016/j.ijhydene.2022.09.047
127. Mourya P, Goswami R, Saini R, et al. Epoxy coating reinforced with graphene-PANI nanocomposites for enhancement of corrosion-resistance performance of mild steel in saline water. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*. 2024;687:133500. DOI:10.1016/j.colsurfa.2024.133500
128. Yan J, Wei T, Shao B, et al. Preparation of a graphene nanosheet/polyaniline composite with high specific capacitance. *Carbon*. 2010;48:487-493. DOI:10.1016/j.carbon.2009.09.066
129. Zhang Q-Y, Yang Y-J, Tang M-Y, et al. Electrochemical preparation and features of newly cross-stacking multi-layered reduced graphene oxide (rGO) and polyaniline (PANI) modified carbon-based electrode. *Current Research in Biotechnology*. 2024;7:100196. DOI:10.1016/j.crbiot.2024.100196
130. Okhay O, Tkach A. Polyaniline-graphene electrodes prepared by electropolymerization for high-performance capacitive electrodes: a brief review. *Batteries*. 2022;8(10):191. DOI:10.3390/batteries8100191
131. Ma B, Zhou X, Bao H, et al. Hierarchical composites of sulfonated graphene-supported vertically aligned polyaniline nanorods for high-performance supercapacitors. *Journal of Power Sources*. 2012;215:36-42. DOI:10.1016/j.jpowsour.2012.04.083
132. Jianhua L, Junwei A, Yecheng Z, et al. Preparation of an amide group-connected graphene-polyaniline nanofiber hybrid and its application in supercapacitors. *ACS Applied Materials and Interfaces*. 2012;4:2870-2876. DOI:10.1021/am300640y
133. Umar Ah, Ahmed F, Ullah N, et al. Exploring the potential of reduced graphene oxide/polyaniline (rGO@PANI) nanocomposites for high-performance supercapacitor application. *Electrochimica Acta*. 2024;479:143743. DOI:10.1016/j.electacta.2023.143743
134. Huang Z, Li L, Wang Y, et al. Polyaniline/graphene nanocomposites towards high-performance supercapacitors: A review. *Composites Communications*. 2018;8:83-91. DOI:10.1016/j.coco.2017.11.005
135. Li Y, Zhao X, Yu P, et al. Oriented arrays of polyaniline nanorods grown on graphite nanosheets for an electrochemical supercapacitor. *Langmuir*. 2013;29:493-500. DOI:10.1021/la303632d
136. Wang DW, Li F, Zhao J, et al. Fabrication of graphene/polyaniline composite paper via in situ anodic electropolymerization for high-performance flexible electrode. *ACS Nano*. 2009;3:1745-1752. DOI:10.1021/nn900297m
137. Huang YF, Lin CW. Facile synthesis and morphology control of graphene oxide/polyaniline nanocomposites via in-situ polymerization process. *Polymer*. 2012;53(13):2574-2582. DOI:10.1016/j.polymer.2012.04.022
138. Gutnik IV, Dyachkova TP, Burakova EA, et al. Polyaniline/mesoporous carbon composites as promising materials for supercapacitors. *IOP Conference Series: Materials Science and Engineering: 3, Synthesis, Production, and Application*. Tambov. 2019;693:012026. DOI:10.1088/1757-899X/693/1/012026
139. Kumar M, Singh K, Dhawan SK, et al. Synthesis and characterization of covalently-grafted graphene-polyaniline nanocomposites and its use in a

- supercapacitor. *Chemical Engineering Journal*. 2013;231:397-405. DOI:10.1016/j.cej.2013.07.043
140. Shen J, Yang C, Li X, et al. High-performance asymmetric supercapacitor based on nanoarchitected polyaniline/graphene/carbon nanotube and activated graphene electrodes. *ACS Applied Materials and Interfaces*. 2013;5:8467-8476. DOI:10.1021/am4028235
141. Yan J, Wei T, Fan Z, et al. Preparation of graphene nanosheet / carbon nanotube / polyaniline composite as electrode material for supercapacitors. *Journal of Power Sources*. 2010;195(9):3041-3045. DOI:10.1016/j.jpowsour.2009.11.028
142. Ali I, Burakov AE, Burakova IV, et al. Polyaniline modified CNTs and graphene nanocomposite for removal of lead and zinc metal ions: kinetics, thermodynamics and desorption studies. *Molecules*. 2022;27(17):5623. DOI:10.3390/molecules27175623
143. Kuznetsova TS, Burakov AE, Pasko TV, et al. Physico-chemical and sorption properties of nanocomposite aerogels based on modified carbon nanotubes and graphene. *Izvestiya vysshih uchebnyh zavedenij. Seriya: himiya i himicheskaya tekhnologiya. = ChemChemTech*. 2023;66(3):66-76. DOI:10.6060/ivkkt.20236603.6726 (In Russ.)
144. Kuznetsova TS, Burakov AE, Burakova IV, et al. Preparation of a polyaniline-modified hybrid graphene aerogel-like nanocomposite for efficient adsorption of heavy metal ions from aquatic media. *Polymers*. 2023;15(5):1101. DOI:10.3390/polym15051101
145. Rattanakunsong N, Bunkoed O. A porous composite monolith sorbent of polyaniline, multiwall carbon nanotubes and chitosan cryogel for aromatic compounds extraction. *Microchemical Journal*. 2020;154:104562. DOI:10.1016/j.microc.2019.104562
146. Wang X, Ouyang J, Wang L, et al. Wood shavings combined with polyaniline and carbon nanotube film for flexible high-performance energy storage devices. *Journal of Energy Storage*. 2024;77:109927. DOI:10.1016/j.est.2023.109927
147. Liu Sh, Chen Y, P.-K. Dorsel P, et al. Facile preparation of nanocellulose/multi-walled carbon nanotube/polyaniline composite aerogel electrodes with high area-specific capacitance for supercapacitors. *International Journal of Biological Macromolecules*. 2023;238:124158. DOI:10.1016/j.ijbiomac.2023.124158
148. Lee KS, Park ChW, Phiri I, et al. New design for Polyaniline@Multiwalled carbon nanotubes composites with bacteria doping for supercapacitor electrodes. *Polymer*. 2020;210:123014. DOI:10.1016/j.polymer.2020.123014
149. Yu T, Zhu P, Xiong Y, et al. Synthesis of microspherical polyaniline/graphene composites and their application in supercapacitors. *Electrochimica Acta*. 2016;222:12-19. DOI:10.1016/j.electacta.2016.11.033
150. Zhang Y, Si L, Zhou B, et al. Synthesis of novel graphene oxide/pristine graphene/polyaniline ternary composites and application to supercapacitor. *Chemical Engineering Journal*. 2016;288:689-700. DOI:10.1016/j.cej.2015.12.058
151. Shao F, Niu Y, Li B, et al. Binary nanosheet frameworks of graphene/polyaniline composite for high-area flexible supercapacitors. *Materials Chemistry and Physics*. 2021;273:125128. DOI:10.1016/j.matchemphys.2021.125128
152. Li B, Li Z, Zhang L, et al. Facile synthesis of polyaniline nanofibers/porous carbon microspheres composite for high performance supercapacitors. *Journal of the Taiwan Institute of Chemical Engineers*. 2017;81:465-471. DOI:10.1016/j.jtice.2017.08.009
153. Zhou J, Sun Y, Zhou Ch, et al. Polyaniline/carbon hybrids: Synthesis and application for alizarin red S removal from water. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*. 2023;676(A):132204. DOI:10.1016/j.colsurfa.2023.132204
154. Ansari MO, Kumar R, Ansari SA, et al. Anion selective pTSA doped polyaniline@graphene oxide-multiwalled carbon nanotube composite for Cr(VI) and Congo red adsorption. *Journal of Colloid and Interface Science*. 2017;496:407-415. DOI:10.1016/j.jcis.2017.02.034
155. Al-Hamry A, Lu T, Bai J, et al. Versatile sensing capabilities of layer-by-layer deposited polyaniline-reduced graphene oxide composite-based sensors. *Sensors and Actuators B: Chemical*. 2023;390:133988. DOI:10.1016/j.snb.2023.133988
156. Aghamiri ZS, Mohsennia M, Rafiee-Pour H-A. Fabrication and characterization of cytochrome c-immobilized polyaniline/multi-walled carbon nanotube composite thin film layers for biosensor applications. *Thin Solid Films*. 2018;660:484-492. DOI:10.1016/j.tsf.2018.06.055
157. Gautam V, Singh KP, Yadav VL. Polyaniline/multiwall carbon nanotubes/starch nanocomposite material and hemoglobin modified carbon paste electrode for hydrogen peroxide and glucose biosensing. *International Journal of Biological Macromolecules*. 2018;111:1124-1132. DOI:10.1016/j.ijbiomac.2018.01.094
158. Shao Y, Dong Y, Bin L, et al. Application of gold nanoparticles/polyaniline-multi-walled carbon nanotubes modified screen-printed carbon electrode for electrochemical sensing of zinc, lead, and copper. *Microchemical Journal*. 2021;170:106726. DOI:10.1016/j.microc.2021.106726
159. Pontes K, Soares BG. Segregated structure of poly (vinylidene fluoride-co-hexafluoropropylene) composites loaded with polyaniline@carbon nanotube hybrids with enhanced microwave absorbing properties. *Synthetic Metals*. 2022;288:117096. DOI:10.1016/j.synthmet.2022.117096
160. Ebrahim S, El-Raey R, Hefnawy A, et al. Electrochemical sensor based on polyaniline nanofibers/single wall carbon nanotubes composite for detection of malathion. *Synthetic Metals*. 2014;190:13-19. DOI:10.1016/j.synthmet.2014.01.021
161. Dhawan SK, Singh N, Rodrigues D. Electromagnetic shielding behaviour of conducting polyaniline composites. *Science and Technology of*

Advanced Materials. 2003;4(2):105-113. DOI:10.1016/S1468-6996(02)00053-0

162. Batool K, Rani M, Osman SM, et al. High electrochemical capacity of novel ternary graphene oxide based PANI/Co₃O₄ nanocomposite as supercapacitor electrode material. *Diamond and Related Materials*. 2024;143:110904. DOI:10.1016/j.diamond.2024.110904

163. Mahato N, Faisal M, Sreekanth TVM, et al. In-situ engineered polycrystalline phases in polyaniline-multiwalled carbon nanotubes composite exhibiting unique mechanism of charge storage. *Materials Letters*. 2023;350:134867. DOI:10.1016/j.matlet.2023.134867

164. Liu S, Chen Y, Dorsel P-KP, et al. Facile preparation of nanocellulose/multi-walled carbon nanotube/polyaniline composite aerogel electrodes with high area-specific capacitance for supercapacitors. *International Journal of Biological Macromolecules*. 2023;238:124158. DOI:10.1016/j.ijbiomac.2023.124158

165. Anukul KTh, Deshmukh AB, Choudhary RB, et al. Facile synthesis and electrochemical evaluation of PANI/CNT/MoS₂ ternary composite as an electrode material for high performance supercapacitor. *Materials Science and Engineering: B*. 2017;223:24-34. DOI:10.1016/j.mseb.2017.05.001

166. Rahman MdM, Shawon MR, Rahman MdH, et al. Synthesis of polyaniline-graphene oxide based ternary nanocomposite for supercapacitor application. *Journal of Energy Storage*. 2023;67:107615. DOI:10.1016/j.est.2023.107615

167. Singu BS, Male U, Srinivasan P, et al. Preparation and performance of polyaniline–multiwall carbon nanotubes–titanium dioxide ternary composite electrode material for supercapacitors. *Journal of Industrial and Engineering Chemistry*. 2017;49:82-87. DOI:10.1016/j.jiec.2017.01.010

168. Thomas L, Pete S, Chaitra K, et al. Facile synthesis of PANI-MWCNT-Ni(OH)₂ ternary composites and study of their performance as electrode material for supercapacitors. *Diamond and Related Materials*. 2020;106:107853. DOI:10.1016/j.diamond.2020.107853

169. Zaghoul MMY, Ebrahim Sh, Anas M, et al. Synthesis and characterization of nanocomposites of polyaniline and polyindole with multiwalled carbon nanotubes for high performance supercapacitor electrodes. *Electrochimica Acta*. 2024;475:143631. DOI:10.1016/j.electacta.2023.143631

170. Lu X, Dou H, Yang S, et al. Fabrication and electrochemical capacitance of hierarchical graphene/polyaniline/carbon nanotube ternary composite film. *Electrochimica Acta*. 2011;56(25):9224-9232. DOI:10.1016/j.electacta.2011.07.142

171. Mezgebe MM, Yan Zh, Wei G, et al. 3D graphene-Fe₃O₄-polyaniline, a novel ternary composite for supercapacitor electrodes with improved electrochemical properties. *Materials Today Energy*. 2017;5:164-172. DOI:10.1016/j.mtener.2017.06.007

172. Huang Ch, Hao Ch, Zheng W, et al. Synthesis of polyaniline/nickel oxide/sulfonated graphene ternary

composite for all-solid-state asymmetric supercapacitor. *Applied Surface Science*. 2020;505:144589. DOI:10.1016/j.apsusc.2019.144589

173. Hao M, Chen Y, Xiong W, et al. Coherent polyaniline/graphene oxides/multi-walled carbon nanotubes ternary composites for asymmetric supercapacitors. *Electrochimica Acta*. 2016;191:165-172. DOI:10.1016/j.electacta.2016.01.076

174. Verma S, Das T, Pandey VK, et al. Nanoarchitectonics of GO/PANI/CoFe₂O₄ (Graphene Oxide/polyaniline/Cobalt Ferrite) based hybrid composite and its use in fabricating symmetric supercapacitor devices. *Journal of Molecular Structure*. 2022;1266:133515. DOI:10.1016/j.molstruc.2022.133515

175. Muhammad Z, Rukhsar A, Sabahat S, et al. Polyaniline-based nanocomposites for electromagnetic interference shielding applications: A review. *Journal of Thermoplastic Composite Materials*. 2021;36(4):089270572110224. DOI:10.1177/08927057211022408

176. Hanifah N, Subadra ST, UI, Hidayat NI, et al. A novel Fe₃O₄/ZnO/PANI/rGO nanohybrid material for radar wave absorbing. *Materials Chemistry and Physics*. 2024;317:129169. DOI:10.1016/j.matchemphys.2024.129169

177. Souto LFC, Soares BG. Electromagnetic wave absorption, EMI shielding effectiveness and electrical properties of ethylene – vinyl Acetate (EVA)/ Polyaniline (PANI) blends prepared by in situ polymerization. *Synthetic Metals*. 2023;298:117441. DOI:10.1016/j.synthmet.2023.117441

178. Xie Zh, Chen H, Xie M, et al. Electrical percolation networks of MWCNT/Graphene/Polyaniline nanocomposites with enhanced electromagnetic interference shielding efficiency. *Applied Surface Science*. 2024;655(51):159613. DOI:10.1016/j.apsusc.2024.159613

179. Goswami RN, Mourya P, Saini R, et al. Polyaniline-wrapped nitrogen-doped graphene nanocomposites as protective functional fillers in epoxy coatings for remarkable enhancement of corrosion inhibition performance. *Progress in Organic Coatings*. 2024;189:108335. DOI:10.1016/j.porgcoat.2024.108335

180. Kang Y, Wang C, Chen C. Preparation of 2D leaf-shaped and 3D flower-shaped sandwich-like polyaniline nanocomposites and application on anticorrosion. *Journal of Applied Polymer Science*. 2020;138(4):49729. DOI:10.1002/app.49729

181. Yuan T, Zhang ZH, Li J, et al. Corrosion protection of aluminum alloy by epoxy coatings containing polyaniline modified graphene additives. *Materials and Corrosion*. 2019;70:1298-1305. DOI:10.1002/maco.201810549

182. Raj GK, Singh E, Hani U, et al. Conductive polymers and composites-based systems: An incipient stride in drug delivery and therapeutics realm. *Journal of Controlled Release*. 2023;355:709-729. DOI:10.1016/j.jconrel.2023.02.017

183. Liu R, Li A, Lang Y, et al. Stimuli-responsive polymer microneedles: A rising transdermal drug delivery system and Its applications in biomedical. *Journal of Drug*

- Delivery Science and Technology.* 2023;88:104922. DOI:10.1016/j.jddst.2023.104922
184. Jose A, Bansal M, Svirskis D, et al. Synthesis and characterization of antimicrobial colloidal polyanilines. *Colloids and Surfaces B: Biointerfaces.* 2024;238:113912. DOI:10.1016/j.colsurfb.2024.113912
185. Sun S, Xu Y, Maimaitiyiming X. 3D printed carbon nanotube/polyaniline/gelatin flexible NH₃, stress, strain, temperature. *Reactive and Functional Polymers.* 2023;190(11):105625. DOI:10.1016/j.reactfunctpolym.2023.105625
186. Wu G, Du H, Cha YL, et al. A wearable mask sensor based on polyaniline/CNT nanocomposites for monitoring ammonia gas and human breathing. *Sensors and Actuators B: Chemical.* 2023;375:132858. DOI:10.1016/j.snb.2022.132858.
187. Matindoust S, Farzi A, Nejad MB, et al. Ammonia gas sensor based on flexible polyaniline films for rapid detection of spoilage in protein-rich foods. *Journal of Materials Science: Materials in Electronics.* 2017;28(11):7760-7768. DOI:10.1007/s10854-017-6471-z
188. Pegu B, Konwar M, Sarma D, et al. Cu nanoparticle anchored highly conducting, reusable multifunctional rGO/PANI nanocomposite: A novel material for methanol sensor and a catalyst for click reaction. *Synthetic Metals.* 2024;301:117516. DOI:10.1016/j.synthmet.2023.117516
189. Sahoo S, Sahoo PK, Sharma A, et al. Interfacial polymerized RGO/MnFe₂O₄/polyaniline fibrous nanocomposite supported glassy carbon electrode for selective and ultrasensitive detection of nitrite. *Sensors and Actuators B: Chemical.* 2020;309:127763-127763. DOI:10.1016/j.snb.2020.127763
190. Jiang Sh, Zhang H, Li Zh, et al. High-sensitivity integrated detector with nanostructured hydrogel electrode for ascorbic acid determination. *Microchemical Journal.* 2023;189:108510. DOI:10.1016/j.microc.2023.108510
191. Morais JPL, Bernardino DV, Batista BdaS, et al. Conductive polymer blend based on polyaniline and galactomannan: Optical and electrical properties. *Synthetic Metals.* 2023;295:117346. DOI:10.1016/j.synthmet.2023.117346
192. Chajanovsky I, Cohen S, Muthukumar D, et al. Enhancement of integrated nano-sensor performance comprised of electrospun PANI/carbonaceous material fibers for phenolic detection in aqueous solutions. *Water Research.* 2023;246:120709. DOI:1016/j.watres.2023.120709
193. Virutkar PD, Mahajan AP, Meshram BH, et al. Conductive polymer nanocomposite enzyme immobilized biosensor for pesticide detection. *Journal of Materials NanoScience.* 2019;6(1):7-12.
194. Gautam V, Singh KP, Yadav VL. Polyaniline/MWCNTs/starch modified carbon paste electrode for non-enzymatic detection of cholesterol: application to real sample (cow milk). *Analytical and Bioanalytical Chemistry.* 2018;410:2173-2181. DOI:10.1007/s00216-018-0880-6
195. Hassan Z, Alsalhi SA, Drissi N, et al. Graphene nanoplatelets-polyaniline composite for the detection of cortisol. *Journal of Physics and Chemistry of Solids.* 2024;191:112031. DOI:10.1016/j.jpics.2024.112031
196. Charekhah R, Jarrahi Z, Darabi M, et al. Bulk heterojunction solar cells based on polyaniline/multi wall carbon nanotube: from morphology control to cell efficiency. *Journal of Materials Science: Materials in Electronics.* 2019;30:26–36. DOI:10.1007/s10854-018-0169-8
197. Yazdi M, Saeidi H, Zarrintaj P, et al. PANI-CNT nanocomposites. In: Mozafari M, Chauhan N. (eds.) *Fundamentals and Emerging Applications of Polyaniline.* Elsevier; 2019. p. 143-163. DOI:10.1016/B978-0-12-817915-4.00009-9
198. Dawo Ch, Iyer PK, Chaturvedi H. Carbon nanotubes/PANI composite as an efficient counter electrode material for dye sensitized solar cell. *Materials Science and Engineering: B.* 2023;297:116722. DOI:10.1016/j.mseb.2023.116722
199. Ma ponya TC, Hato MJ, Somo TR, et al. Polyaniline-based nanocomposites for environmental remediation. In: *Trace metals in the environment – new approaches and recent advances.* IntechOpen; 2021. DOI:10.5772/intechopen.82384
200. Mondal S, Rana U, Das P, et al. Network of polyaniline nanotubes for wastewater treatment and oil/water separation. *ACS Applied Polymer Materials.* 2019;1(7):1624-1633. DOI:10.1021/acsapm.9b00199
201. Kumar A, Kumar V, Awasthi K. Polyaniline-carbon nanotube composites: preparation methods, properties, and applications. *Polymer-Plastics Technology and Engineering.* 2018;57:70-97. DOI:10.1080/03602559.2017.1300817
202. Samadi A, Xie M, Li J, et al. Polyaniline-based adsorbents for aqueous pollutants removal: A review. *Chemical Engineering Journal.* 2021;418:129425. DOI:10.1016/j.cej.2021.129425
203. Dyachkova TP, Melezhyk AV, Morozova ZhG, et al. The study of absorption of copper and nickel ions by polyaniline and its nanocomposite with carbon nanotubes. *Vestnik Tambovskogo gosudarstvennogo tekhnicheskogo universiteta.* 2012;18(4):1067-1073. (In Russ.)
204. Dyachkova TP, Anosova IV, Galunin EV, et al. Synthesis of composites based on polyaniline-modified dispersed nanocarbon supports and prospects of their application as sorbents. *Nano Hybrids and Composites.* 2017;13:135-141. DOI:10.4028/www.scientific.net/NHC.13.135
205. Wai MA, Marchenko MV, Troshkina ID, et al. Scandium adsorption from sulfuric-chloride solutions by PANI/CNTs Nanocomposite. *Advanced Materials and Technologies.* 2019;4(16):58-65. DOI:10.17277/amt.2019.04.pp.058-065
206. Dayyoub T, Maksimkin AV, Kaloshkin S, et al. The structure and mechanical properties of the uhmwpe films modified by the mixture of graphene nanoplates with

polyaniline. *Polymers*. 2019;11(1):23. DOI:10.3390/polym11010023

207. Dyachkova T, Gutnik I, Nagdaev V, et al. Studying the surface of UHMWPE films modified with

graphene nanoplatelets using a Raman mapping method. *Fullerenes, Nanotubes and Carbon Nanostructures*. 2020;28(7):561-564. DOI:10.1080/1536383X.2020.1724103

Information about the authors / Информация об авторах

Irina V. Gutnik, Cand. Sc. (Eng.), Associate Professor, Tambov State Technical University (TSTU), Tambov, Russian Federation; ORCID 0000-0003-1236-7187; e-mail: i.v.gutnik@yandex.ru

Tatyana P. Dyachkova, D. Sc. (Chem.), Professor, TSTU, Tambov, Russian Federation; ORCID 0000-0002-4884-5171; e-mail: dyachkova_tp@mail.ru

Elena A. Burakova, D. Sc. (Eng.), Associate Professor, TSTU, Tambov, Russian Federation; ORCID 0000-0001-8927-7433; e-mail: elenburakova@yandex.ru

Evgeny N. Tugolukov, D. Sc. (Eng.) Professor, TSTU, Tambov, Russian Federation; ORCID 0000-0003-1766-3786; e-mail: tugolukov.en@mail.ru

Artyom V. Rukhov, D. Sc. (Eng.), Head of the Department "Chemistry and Chemical Technologies", TSTU, Tambov, Russian Federation; ORCID 0000-0001-9194-8099; e-mail: artem1@inbox.ru

Georgy A. Titov, Student, TSTU, Tambov, Russian Federation; ORCID 0000-0002-3930-0559; e-mail: bombercd1@mail.ru

Гутник Ирина Владимировна, кандидат технических наук, доцент, Тамбовский государственный технический университет (ТГТУ), Тамбов, Российская Федерация; ORCID 0000-0003-1236-7187; e-mail: i.v.gutnik@yandex.ru

Дьячкова Татьяна Петровна, доктор химических наук, профессор, ТГТУ, Тамбов, Тамбов, Российская Федерация; ORCID 0000-0002-4884-5171; e-mail: dyachkova_tp@mail.ru

Буракова Елена Анатольевна, доктор технических наук, доцент, ТГТУ, Тамбов, Российская Федерация; ORCID 0000-0001-8927-7433; e-mail: elenaburakova@yandex.ru

Туголуков Евгений Николаевич, доктор технических наук, профессор, ТГТУ, Тамбов, Российская Федерация; ORCID 0000-0003-1766-3786; e-mail: tugolukov.en@mail.ru

Рухов Артем Викторович, доктор технических наук, профессор, заведующий кафедрой, ТГТУ, Тамбов, Российская Федерация; ORCID 0000-0001-9194-8099; e-mail: artem1@inbox.ru

Титов Георгий Анатольевич, студент, ТГТУ, Тамбов, Российская Федерация; ORCID 0000-0002-3930-0559; e-mail: bombercd1@mail.ru

Received 30 April 2024; Accepted 27 May 2024; Published 04 July 2024



Copyright: © Gutnik IV, Dyachkova TP, Burakova EA, Tugolukov EN, Rukhov AV, Titov GA, 2024. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).